



HAL
open science

Nanoplasmonics for efficient gas sensing and detection

Benjamin Demirdjian, Igor Ozerov, Frédéric Bedu, Alain Ranguis, Claude R Henry

► **To cite this version:**

Benjamin Demirdjian, Igor Ozerov, Frédéric Bedu, Alain Ranguis, Claude R Henry. Nanoplasmonics for efficient gas sensing and detection. 5th Nanophotonics and Micro/Nano Optics International Conference 2022, Oct 2022, Paris, France. . hal-03853307

HAL Id: hal-03853307

<https://cnrs.hal.science/hal-03853307v1>

Submitted on 17 Nov 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Nanoplasmonic sensing for efficient gas sensing and detection

B. Demirdjian, I. Ozerov, F. Bedu, A. Ranguis, C. R. Henry


Aix-Marseille University, CNRS, CINaM UMR 7325, 13288 Marseille, France



NANOSENSORS BASED ON LSPR

Extraordinary optical properties of noble-metal nanoparticles :

→ development of (chemical, biological, ...) sensitive nanosensors




Localized surface plasmon resonance (LSPR) extinction peak : collective oscillation of electrons of an illuminated metal nanoparticle (NP)

The minimum of reflected light corresponds to a maximum of absorbance


Analyst, 2020, 145, 3776-3800

DIRECT NANOPLASMONIC SENSING (DNPS)

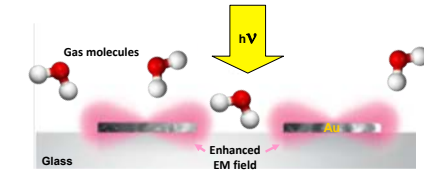


Gas adsorption on gold disks modify their dielectric properties

→ a wavelength shift of the LSPR response of the gold disk sensor



INDIRECT NANOPLASMONIC SENSING (INPS)

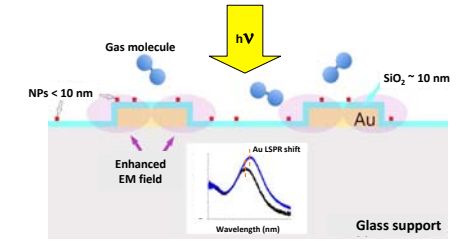

NPs react with gas molecules → modification the dielectric properties at the NP surface
→ LSPR shift of the underlying Au detector.

FDTD AND OPTIMISATION OF GOLD NANODISKS PARAMETERS

FDTD Simulations (Ansys Lumerical) :

→ Parameters (p, h, d) giving the best theoretical S/N (time saving for nanofabrication)


→ Interpreting LSPR spectra

Au disks sensors / borosilicate glass window (750 x 750 x 750 nm³)

Computational domain :
ΔX = ΔY = 300 nm, ΔZ = 400 nm.

Periodic boundary conditions in X and Y
Perfectly Matched Layers in Z direction to avoid unwanted reflections.

Optical source = incident plane wave perpendicular to the surface of the structure (XY plane) propagating in the negative sense of the Z direction



<p> = 300 nm
<h> = 25 nm
d = 150 nm

GOLD NANODISKS FABRICATION: EBL PROCESS (PLANETE)

Sample holder = borosilicate glass window, e = 1 mm, Ø = 25 mm
Cleaning: acetone + US, then Isopropanol + US, EDI rinsing, oxygen plasma oven at 150°C (300 W during 10 min)

PMMA spin-coating (resin 950 K at 4%, speed : 4000 rpm, e = 270 nm annealing 10 min at 170°C)

Gold layer deposition (5 nm) to remove the charges (Edwards 306)


Gold film irradiated with an electron beam (Raith PIONEER)
Area of 1 x 1 mm²

Revelation in acetone (Au is removed) then with MIBK/IPA 1 : 3 during 45 s
Then with IPA during 45 s (→ holes in the resin)

Cr and Au evaporation within the PMMA resin (Edwards 306)
e_{Cr} = 2 nm, e_{Au} = 20 nm
Lift-off of the resin (acetone + US)

→ Precise control of the shape, the size and the pitch of gold nanodisks


SOOT DEPOSITION ON GOLD NANODISKS: DROPLET DEPOSITION

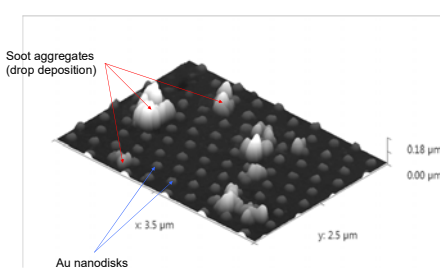

AFM image (tapping mode) - AFM PSIA XE-100

INPS: WATER ADSORPTION ON HYDROPHILIC SOOT PARTICLES

The Journal of Physical Chemistry Letters 6 (2015) 4148-4152

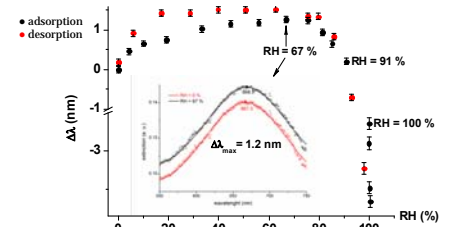


• Highly sensitive sensor → detection of about 2/100 of a water ML !
• At RH > 70 % → peculiar blue shift ! (Δλ_{min} = -3.7 nm)
• Desorption: small hysteresis → porosity

BLUE SHIFT ? → MODELISATION (A. KARAPETYAN)

RH → hydrophilic soot aggregates collapse into + dense structures (Mikhailov et al., J Geophys. Res. 2006, 111, D07209)

→ RH = 100 % soot aggregates are more compact:
• higher mass fractal dimension
• smaller gyration radius
• higher n and k values

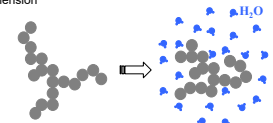


Simulations: analytical Born and Wolf equations → absorbance of the thin multilayers system C/SiO₂/gold/glass

With a thinner C layer (-10 nm) and a higher n value (+0.1):
→ Δλ = -4 nm (- exp. value)

DNPS: WATER ADSORPTION ISOTHERM ON BARE GOLD NANODISKS


Langmuir 34 (2018) 5381-5385

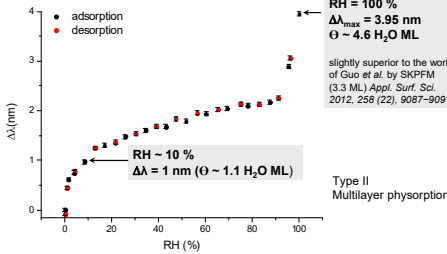

Type II
Multilayer physisorption


High sensitivity: error bars on Δλ ~0.04 nm ~ 4/100 H₂O ML ! (equation (1))
Reversibility: no chemisorption of water on gold (good agreement with Heras et al., Z. Phys. Chem. 129, 11-20 1982)

PT NPS FABRICATION AND TEM OBSERVATIONS (A. ALTIE, D. CHAUDANSON)

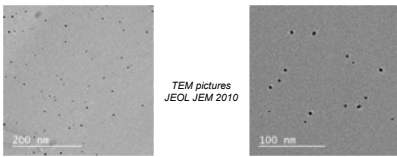


- Chemical synthesis (plasmonic sample immersed in Pt(acac)₃ + chloroform)
- Reduction (CO, H₂) + heating treatment (200 °C) → transfer HV reactor
- Pt NPs cubic shape
• d = 3.0 ± 1 nm
• θ_s = n_s d² = 0.52 % (very low !)

QMS TO FOLLOW CO OXIDATION - QUANTITATIVE MEASUREMENTS

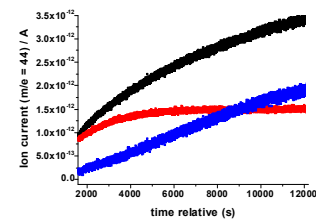

• QMS → monitoring the CO₂ production during CO oxidation on Pt NPs (T = 443 K, X_{CO} = P_{CO} / (P_{CO} + P_{CO₂)) = 0.25)}


• CO₂ production by the plasmatic sample itself (blue) since the contribution from the bare HV reactor (red) has been subtracted.

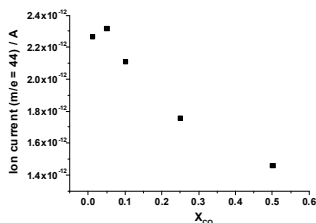

→ the maximum of the steady state CO₂ production is obtained for X_{CO} = 0.05 in agreement with the work of Langhammer et al. (ACS Nano 2019, 13, 6090-6100) on large (70 nm) single Pt particles at 473 K


INPS: OXYGEN AND CO ADSORPTION : ANALOGY Δλ/Δθ

ACS Omega 6 (2021) 13398-13405

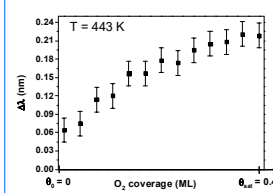

Our INPS measurements:
Δλ > 0 and increases with oxygen coverage

Error bars = lower limit of detection = 0.04 ML !!!

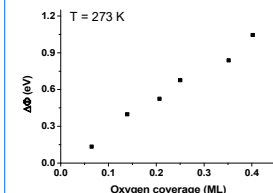


Literature → work function measurements on polycrystalline Pt*

Δθ > 0 and increases with oxygen coverage


→ oxygen is irreversibly adsorbed on Pt NPs until the saturation coverage Θ ~ 0.4 ML

*Norton, Surf. Sci. 1975, 47, 98-114

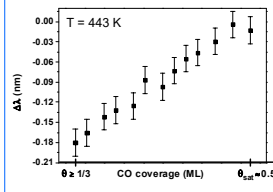

Our INPS measurements :
Δλ < 0 and increases when 0.3 < Θ < 0.5 ML

Error bars = lower limit of detection = 0.04 ML !!!

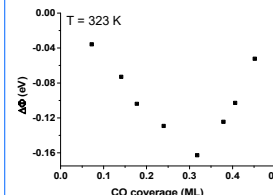

Literature → work function measurements on Pt(111)* :

Δθ < 0 and increases when 0.3 < Θ < 0.5 ML

→ CO is reversibly adsorbed on Pt NPs until the saturation coverage Θ ~ 0.5 ML

*Ertl et al. Surf. Sci. 1977, 64, 393-410

CONCLUSIONS AND OUTLOOKS

Nanoplasmonic sensing :

Quantitative + very sensitive probe: a few hundredths of a ML of adsorbed gas !

Large (P, T) domains for gas sensing, adsorption, reactivity, catalysis ...

Non destructive probe (compare to other probes)

Outlooks :

Improve the LSPR signal (morphology, coupling ...) - FDTD calculations

Increase the density of NP's for INPS (e-beam UHV evaporation)

Theoretical investigation of analogy Δλ/Δθ (shown for the 1st time)

